

V. Rotolo, M. L. De Caro, A. Giordano & F. Palla

Solunto archaeological park in Sicily: life under mosaic tesserae*

Abstract

Rotolo, V., De Caro, M. L., Giordano, A. & Palla, F.: Solunto archaeological park in Sicily: life under mosaic tesserae. — Boccone 28: 115-127. 2019. — ISSN: 1120-4060 printed, 2280-3882 online.

Biodeterioration is a complex process induced by the growing and metabolic activity of a wide range of macro and microorganisms, becoming a revelling problem also for the mosaic tesserae of “Casa di Leda” in the Greco - Roman site of Solunto in Sicily.

In this case-study, a thick biofilm inducing a deep alteration of mortar and consequently the mosaic tesserae detachment has been highlighted during the restoration plan.

The biofilm microbial consortium has been investigated by an integrate approach based on Microscopy analysis (O.M., C.L.S.M.), in vitro culture (Nutrien and Saboraud media) and molecular biology investigation (DNA target sequence amplification, sequencing, sequence analysis).

A microbial diversity has been revealed belonging to bacteria (*Bacillus*) and fungi (*Alternaria*, *Aspergillus*), besides cyanobacteria (*Chroococcus*) and green algae (*Chlorella*).

In order to control the biofilm colonization two essential oils (EO), *Thymus vulgaris* and *Origanum vulgare*, have been utilized and their antimicrobial activity, preliminarily in vitro (agar disc diffusion methods) and after ex situ and in situ evaluated. This experimentation is aimed at identifying and implementing green biocides for the control of microbial colonization, a promising technology with a reduced impact on human health and environment, able to replace traditional biocide action.

Key words: biodeterioration, microscopy analysis, in vitro colture, molecular biology.

Introduction

Stone artworks biodeterioration is related to the combination of biological colonization and environmental factors, as happen in archaeological areas, where complex *biofilm* have been frequently revealed (Thomas & Demas 2013; Marzano & Métraux 2018).

Concerning inorganic specimens, the first colonizers are represented by pioneered photoautotrophic organisms, such as cyanobacteria, algae and lichens, but also oligotrophic or poichilotrophic microbial groups, such as some fungi and chemo-lithotrophic bacteria (i.e. using as oxidation inorganic compounds) have been identified; converting the substrate

*Article first published online on 20 December 2018 in Flora Mediterranea 28: 233-245.

and helping the colonization of other heterotrophic organisms (Tiano & al. 1995; Warscheid & Braams 2000; Caneva & al. 2007).

Moreover, the association as *biofilm* confers a character of resistance to the biocenoses involved (Flemming 1993), becoming problematic to remove (Chorianopoulos 2008).

In this case-study, biofilm was not straightforward seen, since it was spread under several tesserae of the *impluvium*, located in the centre of the “Casa di Leda” *peristylo*, in Solunto (Palermo, Italy) one of the archaeological-park in Mediterranean basin (Marzano & Métraux 2018). Combining biological and biotechnological approaches (Palla & al. 2010, 2013; Di Carlo & al. 2016; Palla & Barresi 2017) microbial taxa such as bacteria, fungi, cyanobacteria and green algae have been identified.

Since the extensive microbial spreading affects both the constitutive materials and the legibility of the artworks (Barranguet & al. 2005), the control of biodeterioration phenomena represents a significant phase in conservation project. In routine practice, microbial colonization is addressed by chemical biocides, which toxicity and persistence in the environment is well known (De La Paz & al. 2006; Guiamet & al. 2006).

In the last decade, in order to develop green conservation strategies, plant products have been applied in prevention and treatment of microbial contaminants (Guiamet & al. 2008; Afifi 2012; Sasso & al. 2013; Fierascu & al. 2014; Stupar & al. 2014; Borrego & al. 2016; Rotolo & al. 2016).

In this study, the antimicrobial activity of two commercial essential oils, *Origanum vulgare* and *Thymus vulgaris*, have been evaluated against microbial species isolated from *biofilms* of floor mosaic tesserae of “Casa di Leda” in the *Greco - Roman site of Solunto* in Sicily (Fig. 1), to control the biodeterioration phenomena, applying novel protocols safe for humans and environment (Rotolo & al. 2017).

Materials and methods

Essential oils (EO)— The *Origanum vulgare* and *Thymus vulgaris* essential oils have been used as pure essence (100%) or diluted solutions (50, 25, 12.5, 6.5 %) in 70% Ethanol.



Fig. 1. Mosaic floor around the *impluvium* in the *peristyle* of Leda’s house, in archaeological park - Solunto, Sicily.

Origanum vulgare, is an aromatic hemicryptophyte, belonging to *Lamiaceae*, native to Europe and in particular in the Mediterranean basin, but today cultivated all over the world. The plant is rich in carvacrol, a phenolic monoterpene with recognized anti-inflammatory and antitumor properties (Burts & al. 2007; McCann & al. 2014).

Thymus vulgaris, is a chamaephyte belonging to *Lamiaceae*, including 250-350 evergreen taxa, native to southern Europe, North Africa and Asia.

The aromatic active molecules have a strong antiseptic and antibacterial properties, they also have digestive, warming, spasmolytic, carminative, diuretic and disinfectant action of the urinary tract. In addition they contain phenolic monoterpenes such as thymol (30-70%) and carvacrol (3-15%), oxides such as cineol and thymol methylesters, alcohols such as borneol, geraniol, linalool, esters such as acetate and linalyl, hydrocarbons such as cymene and terpinen (Mitsch & al. 2004; Bolukbasi & al. 2007).

Sampling.— Biofilm aliquots were collected by sterile scalpel or swab, and directly observed by optical microscopy or utilized for *in vitro* culture and molecular investigations.

Microscopy observation.— Cyanobacteria and microalgae, as well as the morphological profile of bacterial and fungal isolated colonies were analysed by Stereo (Wild-M1B, 14X) or Fluorescent (DMR-Leica, 40X) microscopes. Conidiophores and conidia fungal structures were observed by Optical Microscope (Leica, 40X), after Lugol's iodine staining (Di Carlo & al. 2016).

In vitro culture.— Sabouraud Dextrose Agar + Chloramphenicol (CAF) and Nutrient Agar plates, seeded by biofilm aliquots, were incubated at 30°C (Palla & al. 2006; Pasquarella & al. 2015); after 24/48 h fungi and bacteria colonies

Microbial DNA extraction.— Each isolated bacterial and fungal colony was lysed at 94°C per 2 min in 20 µl of 1X T.E. (10 mM TRIS-HCl pH 7,5 / 1 mM EDTA), extracting the genomic DNA by the *Genomic DNA purification* and *Gene JET Genomic DNA purification* kits (Fermentas).

Polymerase Chain Reaction (PCR) – Genomic DNA molecules were utilized as template for *in vitro* amplification (Polymerase Chain Reaction) of target ribosomal-DNA sequences: 16S-rDNA gene or Internal Transcribed Sequence (ITS – rDNA), specific for bacteria or fungi.

ITS-PCR reactions were carried out by the following oligonucleotides as primers, bacteria: ITS1= 5'-GTCGTAACAAGGTAGCCGT-3' and ITS2= 5'-GCCAAGGCATCCACC-3'; fungi: ITS4 = 5' - TCCTCCGCTTATTGATATGC-3' e ITS1 = 5' -CTTGGTCATTTAGAGGAAGTAA - 3' (Cardinale & al. 2004).

PCR products were analysed by 2% Agarose gel electrophoresis, nucleotide composition determined by MWG Operon Sequencing Service and sequences comparison performed by BLAST platform (Altschul & al. 1997; Palla & al. 2010, 2013; Palla 2012; Palla & Barresi 2017).

Evaluation of antimicrobial activity.— *In vitro* assay: agar disc diffusion method was performed utilizing paper disc (6 mm in diameter), wetted with 10µl of each EO at differ-

ent concentrations (100%, 50%, 25%, 12.5%, 6.25%) and placed onto the surface of Nutrient or Sabouraud agar (90 mm Petri dish), previously seeded by 1×10^6 CFU/mL - bacterial cells or 1×10^4 conidia/mL - conidia suspension (Borrego & al. 2012).

Control assays were performed wetting the paper disc with 70% Ethanol or 0.2% (vol/vol) Benzalkonium chloride + chlorhexidine (BC, one of the frequently used commercial biocides).

After incubation at 30°C for 24/48 h, confluent microbial growth was observed and the diameter (mm) of growth inhibition areas was measured (Balouiri & al. 2016; Rotolo & al. 2016); each test was performed in triplicate.

Ex situ assay: the antimicrobial activity of the two essential oils was also evaluated exposing the biofilm to the volatile compounds. Particularly, eleven colonized tesserae, gathered from specific areas of *impluvium* were placed on paper discs (60 mm, Whatman) into equal in diameter sterile Petri dishes, soaked with: *i*) *Oregano* (100, 50, 15%) EO; *ii*) *Thyme* (100, 50, 15%) EO; *iii*) Biotin-R (100, 50, 15%); *iv*) Ethanol (70%); Petri dishes were sealed by Parafilm membrane (Heathrow Scientific) to prevent evaporation phenomena. The effect of EOs was evaluated after 72h and up to 7 days, analysing both biofilm green pigmentation and auto-fluorescence (MD Fluorescent Microscope, Leica).

In situ assay: biocide activity was also directly evaluated on selected (eleven) *peristyle* mosaic areas. As performed in laboratory assays, differently concentrated Essential Oils (100, 50, 15%) and Controls (100, 50, 15% Biotin-R or 70% Ethanol) solutions were injected (by sterile needle/syringe) through interstitial mortar tesserae.

Results

In order to characterize the microbial species constituting the pigmented *biofilm* revealed below the mosaic tesserae (Fig. 2), an integrated approach was applied (Palla & Barresi 2017). Particularly, a complex microbial community with prevalence of cyanobacteria, belonging to the genus *Chroococcus* and green algae such as *Chlorella* (Fig. 3), was observed by Optical Microscopy. Through *in vitro* culture and molecular investigations, the presence of bacteria, *Bacillus* sp. pl. (Fig. 4) and fungi, *Alternaria* (Fig. 5) sp. and *Aspergillus* sp. (Fig. 6) have been also identified.

The characterization of microbial consortium components is strictly related to the control of microbial spreading, accordingly to the biocide product that will be applied. The aim of this study was also the set-up of alternative biocides, as plant essential oils, less invasive/dangerous than commercial chemical compounds (Guiamet & al. 2008; Afifi 2012; Sasso & al. 2013; Fierascu & al. 2014; Stupar & al. 2014; Borrego & al. 2016; Rotolo & al. 2016).

Performing *in vitro* agar diffusion disc method, different antimicrobial effects of EOs and Controls solutions were defined against *Bacillus* sp. p.l, *Alternaria* sp. and *Aspergillus* sp. colonies, basing on inhibition-halo diameter (Tab.1)

Particularly, *in vitro* assays highlight a stronger antimicrobial activity EOs, as showed in Fig.7a, per *Oregano* solutions (50, 25, 12,5%) versus *Bacillus* sp., compared to the activity of commercial biocide Benzalkonium Chloride solutions (100, 6.25%), showed in fig. 7b.



Fig. 2. Pigmented *biofilm* revealed below the mosaic tesserae in some area of the Leda's house *peristyle*.

Similar strength is showed by *Oregano* solutions (100, 12.5%) vs *Aspergillus* sp. (Fig. 8a) and *Alternaria* sp. (Fig. 8b) colonies, significantly greater comparing the inhibition halo produced by 12.5% Benzalkonium Chloride solution against *Aspergillus* sp. (Fig. 9a) and *Alternaria* sp. (Fig. 9b).

The *ex situ* assays were performed exposing the mosaic-colonized tesserae to the volatile compounds of *Oregano* or *Thyme* EOs, analysing the biofilm after 7 days (will be assessed up one year). As showed in Fig. 10, a different pigmentation can be distinguished between control (D = no-biocidal compound) and treated samples (A= Biotin-R; B= Thyme-EO=; C= Oregano-EO), allowing us to hypothesize that the lack of green pigmentation is related to the reducing in biofilm photosynthetic activity; related Fluorescent Microscope observations performed by Zeiss-Axioskop 2-Plus, are showed in Fig. 11. It is evident only a background of fluorescence in treated samples A, B, C, while defined biological structures are evident in no-treated sample D.

Finally, *in situ* tests were performed injecting below the tesserae, *Oregano* or *Thyme* EOs solutions (100, 50, 15%), through the interstitial space. As showed in Fig. 12, a clear effect on biofilm was revealed for the 15% *Thyme* EO solution, concentrically diffused

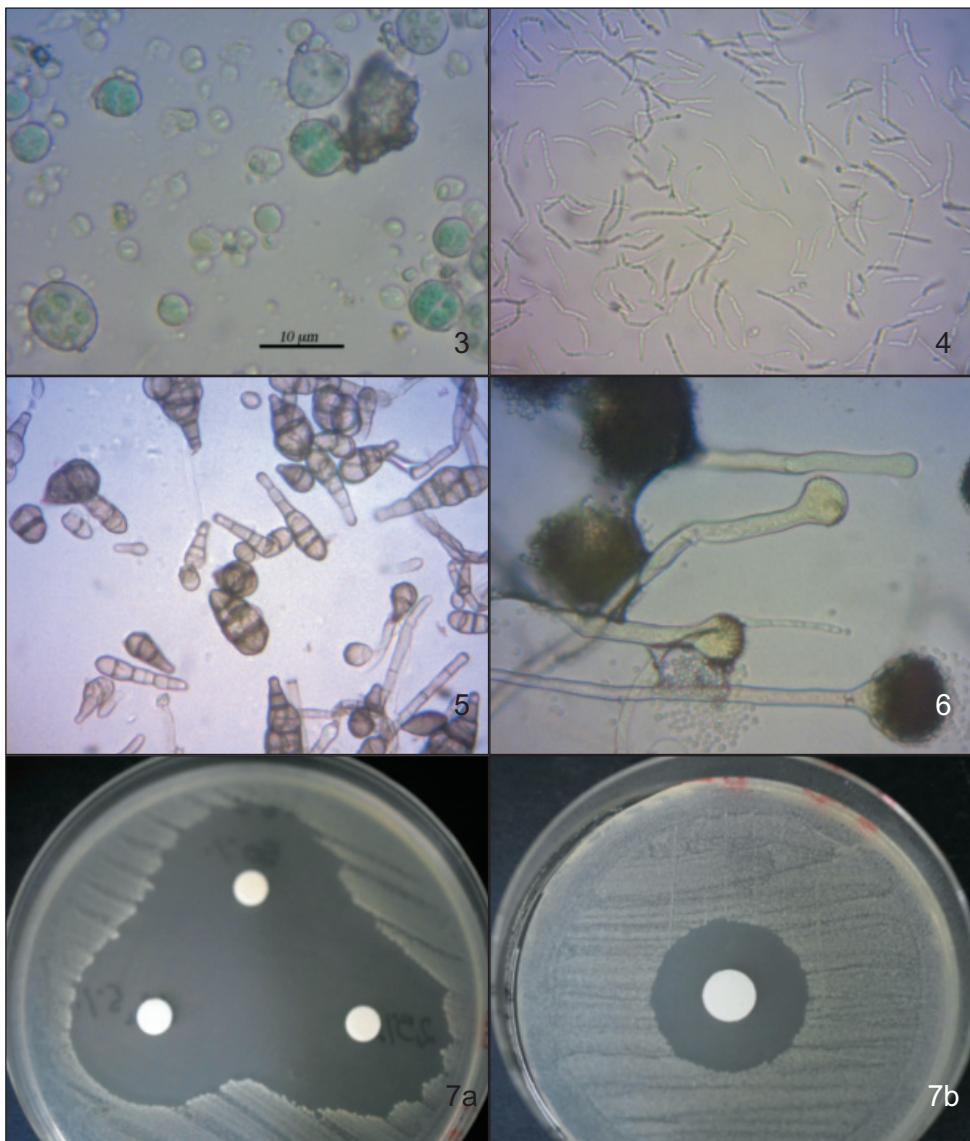


Fig. 3. *Chlorella* sp. colonies observed by Optical Microscope (Leica, 40 \times magnification).

Fig. 4. *Bacillus* sp. bacterial cells observed by Optical Microscope (Leica, 40 \times magnification).

Fig. 5. *Alternaria* sp. spore structure, observed by Optical Microscope (Leica, 40 \times magnification), after Lugol's staining.

Fig. 6. *Aspergillus* sp. conidiophores and spore structures, observed by OM (Leica, 40 \times magnification), after Lugol's staining.

Fig. 7a. Antimicrobial activity of *Oregano* solutions (50.0, 25.0, 12.5%) versus *Bacillus* sp., the confluent inhibition halos prove a strong activity of EO.

Fig. 7b. Antimicrobial activity of the commercial biocide, Benzalkonium Chloride (6.25%) solution, a confluent inhibition halo is show.

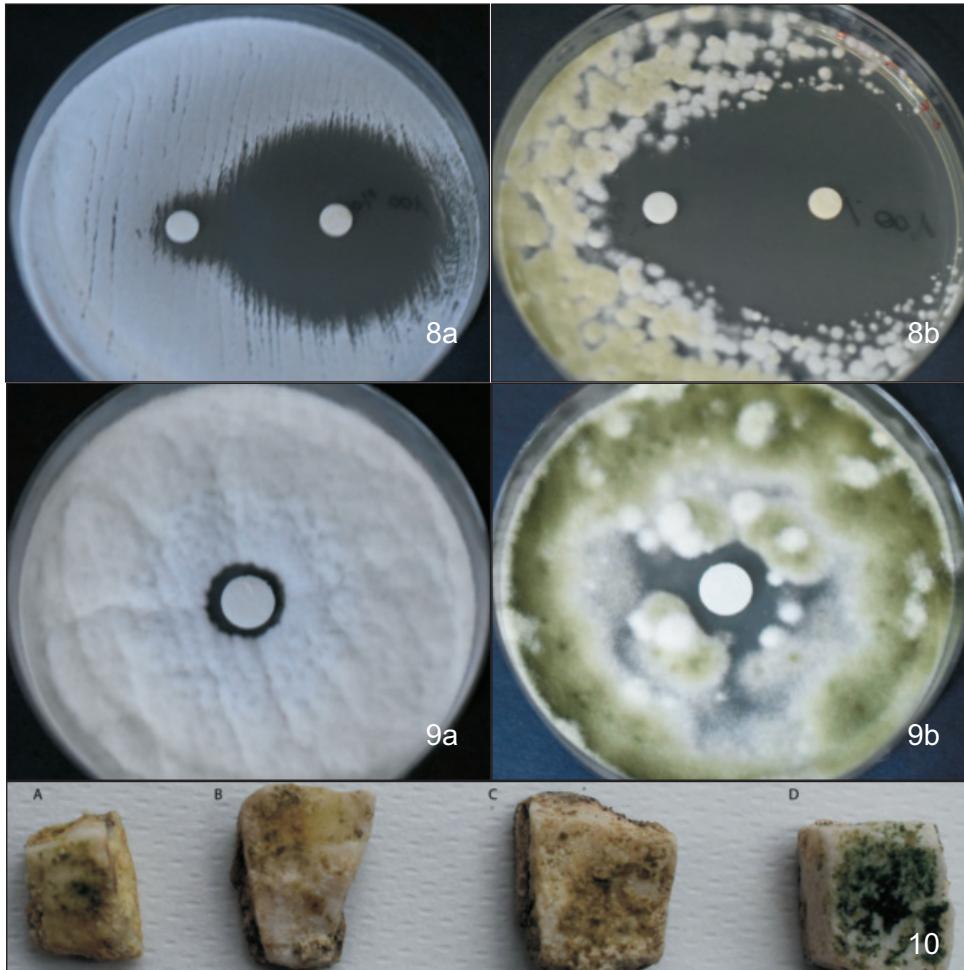


Fig. 8a. Inhibition halo produced by *Oregano* solutions (100, 6.25%) vs *Aspergillus* sp.

Fig. 8b. Inhibition halo produced by *Oregano* solutions (100, 6.25%) vs *Alternaria* sp.

Fig. 9a. Inhibition halo produced by 6.25% Benzalkonium Chloride solution against *Aspergillus* sp.

Fig. 9b. Inhibition halo produced by 6.25% Benzalkonium Chloride solution against *Alternaria* sp.

Fig. 10. *Ex situ* assays. Effect of volatile compounds of Oregano or Thyme EOs, after 7 days of exposure, on the biofilm of mosaic-colonized tesserae: A= Biotin-R (commercial biocide); B= Thyme-EO; C= Oregano-EO; D= no-biocidal compound.

with respect to the injection point (highlighted as red line). Particularly, the biofilm came in contact with the EO solution showed a loss in pigmentation, while a vital green colour is still present in the portion not reached by the oil solution (pointed by a red asterisk). Instead, the 15% *Oregano* OE treatment does not show similar effect, may be related to the presence of inhibitory substances in the completely degraded bedding mortar.

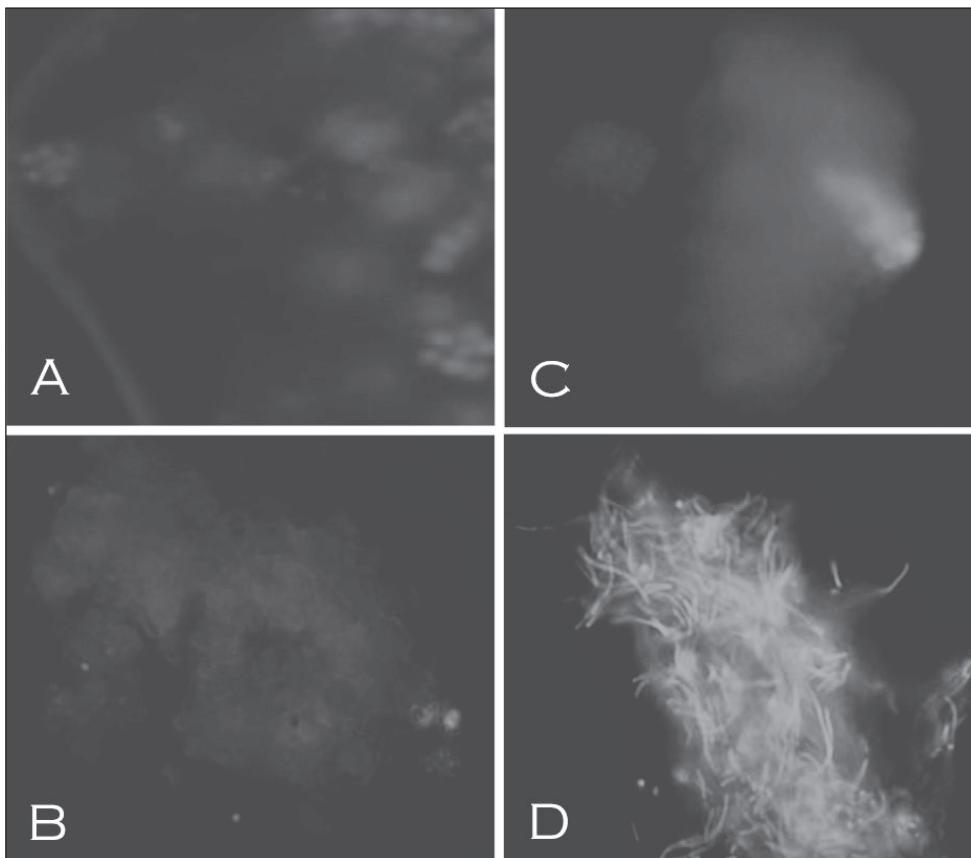


Fig. 11. *Ex situ* assays. The lack of biofilm photosynthetic activity, observed by Zeiss-Axiokop 2-Plus Fluorescent Microscope observations. Corresponding to Fig.10 samples: A= Biotin-R (commercial biocide); B= Thyme-EO; C= Oregano-EO; D= no-biocidal compound (40 \times magnification).

Discussions and Conclusions

The rich distribution of archaeological assets in the Mediterranean basin, their cultural, artistic, religious significance and high social impact, highlight the requirement of dedicated conservation strategies. The identification of the different factors (biological, chemical, physical) able to induce structural and compositional changes (Warscheid 2000) is of fundamental importance in defining suitable fruition, maintenance and conservation policies.

The role played by micro-organisms in the processes of cultural heritage deterioration (biodeterioration) has been widely demonstrated: growth, development and metabolic activities can bring physical-chemical and aesthetic damage to works of art, inducing negative consequences for their conservation (Fort & al. 2006).

Many species of microorganisms (bacteria, fungi, unicellular algae) can find favourable conditions for their development both on statues and monumental works and on archaeo-

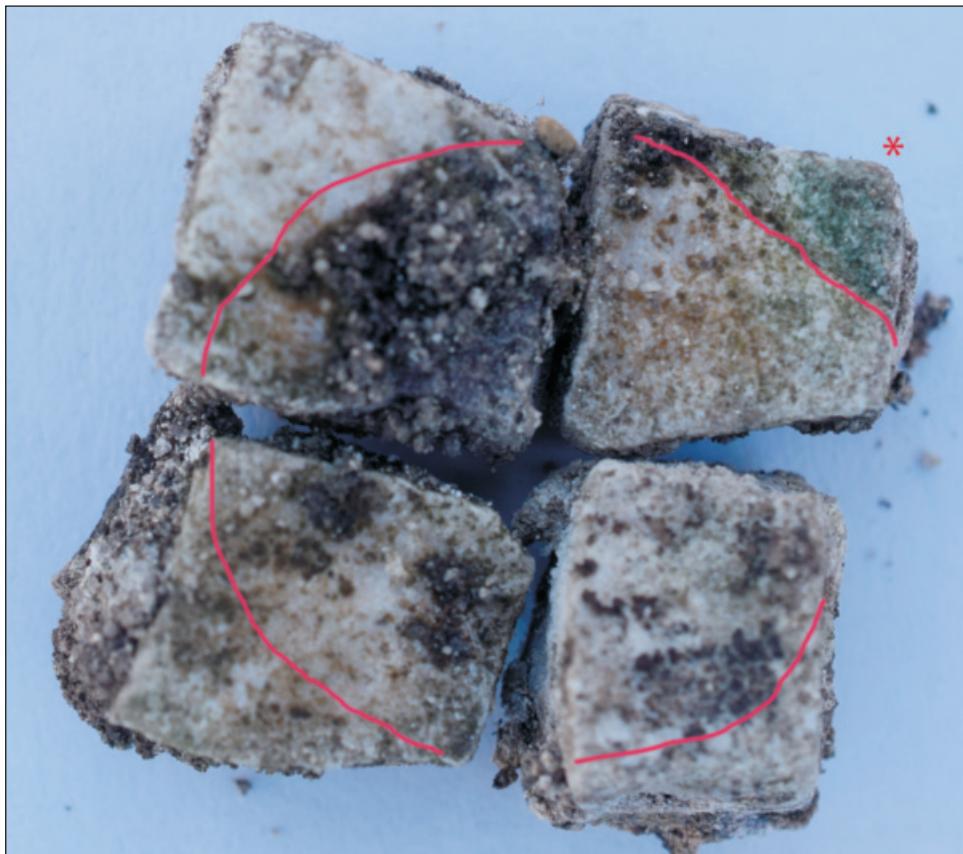


Fig. 12. *In situ* assays. Mosaic tesserae after treatment with 15% *Thyme* solution, concentrically diffused with respect to the injection point (highlighted as red line), a lost in pigmentation is clearly recognizable. A vital green colour is still present in the portion not reached (pointed by an asterisk).

logical remains (Kovacik 2000), as the mosaic tesserae of “Casa di Leda” - Greco - Roman Solunto archaeological site park, Sicily.

Particularly, a thick *biofilm* inducing a deep alteration of mortar and consequently the mosaic tesserae detachment has been identified during the restoration activities.

The *biofilm* has been characterized through optical microscopy, *in vitro* culture and molecular biology techniques, allowing the identification of microbial taxa as *Bacillus* sp., *Alternaria* sp., *Aspergillus* sp., as well as cyanobacteria, *Chroococcus* sp. and green algae, *Chlorella* sp. These microorganisms are considered biodeteriogens, able to induce precipitation of mineral crystals or promoting pH changes, causing damage on stonework surface (Sanchez-Moral & al. 2003; Albertano & al. 2003).

In this study new biocompatible products to control *biofilm* growth have been also assessed, evaluating the antimicrobial activity of two commercial essential oils, *Origanum vulgare* and *Thymus vulgaris*.

Table 1. *Agar disc diffusion* method. Average inhibition halo diameter (mm) of EOs (*O. vulgare*, *T. vulgaris*) Antimicrobial activity: Positive ≥ 9 mm; Moderate: 6 - 9 mm; Negative ≤ 6mm; *total growth inhibition. Benzalkonium chloride + chlorhexidine and Ethanol solutions were the controls.

Essential olis	Conc. (%)	<i>Bacillus</i> sp. pl.	<i>Alternaria</i> sp.	<i>Aspergillus</i> sp.
<i>Origanum vulgare</i>	100	*	60	50
	50.0	42	49	45
	25.0	40	48	46
	12.5	39	38	35
	6.25	28	16	16
<i>Thymus vulgaris</i>	100	*	*	*
	50.0	*	*	*
	25.0	*	*	*
	12.5	48	*	*
	6.25	30	36	32
<i>Benzalkonium chloride + chloroexidine</i>	0.2% (vol/vol)	12	6	8
<i>Ethanol</i>	70%	3	1	1

The results of *agar disc diffusion* assays are summarized in Table 1, showing a strong antimicrobial activity of both essential oils against bacterial and fungal colonies, consistent with the dedicated literature (Reichling & al. 2009; Stupar & al. 2014; Casiglia & al. 2015), although little is known about the permanence and application methods of EOs (Salem & al. 2014; Noshyutta & al. 2016).

In this case study *Origanum vulgare* and *Thymus vulgaris* EOs solution (100, 50, 15 %) have been tested *in situ*, on mosaic tesserae of “Casa di Leda”, after seven days of application.

Particularly, *Thymus vulgaris* 15% EO solution has proven to be the best diffused, strongly influencing the *biofilm* liveliness (Fig. 12).

Although further studies are needed to set up a standard protocol, according to these and previously result (Rotolo & al. 2016, 2017), we hypothesize the use of OEs to contrast microbial colonization, representing valid alternatives to traditional biocides, without negative environmental impacts and respecting the human health, in accordance with modern restoration strategies.

Acknowledgements

Authors thanks Dr. Laura Di Leonardo and Regione Siciliana Assessorato Beni Culturali e dell'Identità Siciliana-Area Archeologica e Antiquarium di Solunto, Palermo, Italy. Authors also thanks Roberta Russo and Marco Chiaramonte, Istituto di Biomedicina e Immunologia Molecolare, CNR – Palermo, for Fluorescent Microscopy observations.

References

- Afifi, H. A. M 2012: Comparative efficacy of some plant extracts against fungal deterioration of stucco ornaments in the Mihrab of Mostafa Pasha, Ribate, Cairo, Egypt. – Amer. J. Biochem. Molec. Biol. **2(1)**: 40-47. doi: 10.3923/ajbmb.2012.40.47
- Albertano, P., Moscone, D., Palleschi, G., Hermosin, B., Saiz-Jimenez, C., Sanchez-Moral, S., Hernandez-Marin, H., Urzi, C., Groth, I., Schroeckh, V., Saarela, M., Mattila-Sandholm, T., Gallon, J. R., Graziottin, E. F., Bisconti, F., Giuliano, R. 2003: Cyanobacteria attack rocks (CATS): Control and preventive strategies to avoid damage caused by Cyanobacteria and associated microorganisms in Roman hypogean monuments.–Pp. 151-162 in: Saiz-Jimenez, C. (ed.) Molecular Biology in Cultural Heritage. – Lisse.
- Altschul, S. F., Madden, T. L., Schäffer, A. A., Zhang, J., Zhang, Z., Miller, W., Lipman, D. J. 1997: Gapped BLAST and PSI-BLAST: a new generation of protein database search programs. – Nucleic Acids Res. **25(17)**: 3389-3402.
- Balouiri, M., Sadiki, M., Ibnsouda, S. K. 2016: Methods for in vitro evaluating antimicrobial activity: a review. – J. Pharm. Anal. **6**: 71-79. doi: 10.1016/j.jpha.2015.11.005
- Barranguet, C., Veuger, B., van Beuseko, S.A.M., Marvan, P., Sinke, J.J., Admiraal, W. 2005: Divergent composition of algal bacterial biofilms developing under various external factors. – Eur. J. Phycol. **40**: 1-8. doi: 10.1080/0967026040009882
- Bolukbasi, S. C. & Erhan, M. K. 2007: Effect of dietary thyme (*Thymus vulgaris*) on laying hen's performance and *Escherichia coli* (*E. coli*) concentration in Feces. – Int. J. Nat. Eng. Sci. **1**: 55-58.
- Borrego, S., Gomez De Saravia, S., Valdes, O., Vivar, I., Battistoni, P., Guiamet P. 2016: Biocidal activity of two essentials oils on fungi that cause degradation of paper documents. – Int. J. Conserv. Sci. **7(2)**: 369-380.
- , Valdés, O., Vivar, I., Lavin, P., Guiamet, P., Battistoni, P., Gómez de Saravia, S. G., Borges, P. 2012: Essential Oils of Plants as Biocides against Microorganisms Isolated from Cuban and Argentine Documentary Heritage. – Int. Schol. Res. Network ISRN Microbiol. **2012**: 1-7. doi: 10.5402/2012/826786
- Burts, S. A., Van Der Zee, R., Koets Ad, P. 2007: Carvacrol Induces Heat Shock Protein 60 and Inhibits Synthesis of Flagellin in *Escherichia coli* O157:H. – Appl. Environ. Microbiol. **73**: 14-15.
- Caneva, G., Nugari, M. P., Salvadori, O. 2007: La biologia vegetale per i beni culturali. Biodeterioramento e conservazione, **1**. – Firenze.
- Cardinale, M., Brusetti, L., Quatrini, P., Borin, S., Puglia, A.M., Rizzi, A. 2004: Comparison of different primer sets for use in automated ribosomal intergenic spacer analysis of complex bacterial communities. – Appl. Environ. Microbiol. **70**: 6147-6156.
- Casiglia, S., Bruno, M., Scandolera, E., Senatore, F., Senatore, F., 2015: Influence of harvesting time on composition of the essential oil of *Thymus capitatus* (L.) Hoffmanns. & Link. growing wild in northern Sicily and its activity on microorganisms affecting historical art crafts. – Arabian J. Chem. **5**: 1-9 doi: 10.1016/j.arabjc.2015.05.017
- Chorianopoulos, N. G., Giaouris, E. D., Skandamis, P. N., Haroutounian, S. A., Nychas, G. J. E. 2008: Disinfectant test against monoculture and mixed-culture biofilms composed of technological, spoilage and pathogenic bacteria: bactericidal effect of essential oil and hydrosol of *Satureja thymbra* and comparison with standard acid- base sanitizers. – J. Appl. Microbiol. **104(6)**: 1586-1596. doi: 10.1111/j.1365-2672.2007.03694.x
- De la Paz, J., Larionova, M., Maceira, M. A., Borrego, S. F., Echevarría, E. 2006: Control of biodegradation using a fraction isolated from leaves of *Ricinus communis* Linn. – Pharmacologyonline **3**: 462-466.

- Di Carlo, E., Chisesi, R., Barresi, G., Barbaro, S., Lombardo, G., Rotolo, V., Sebastianelli, M., Travagliato, G., Palla, F. 2016: Fungi and Bacteria in Indoor Cultural Heritage Environments: Microbial-related Risks for Artworks and Human Health. – *Environ. Ecol. Res.* **4(5)**: 257-264. doi: 10.13189/eer.2016.040504
- Fierascu, I., Ion, R.M., Radu, M., Bunghez, I.R., Avramescu, S.M., Fierascu, R.C. 2014: Comparative study of antifungal effect of natural extracts and essential oils of *Ocimum basilicum* on selected artefacts. – *Rev. Roum. Chim.* **59(3-4)**: 207-211.
- Flemming, H. C. 1993: Biofilms and environmental protection. – *Water Sci. Technol.* **27**: 1-10.
- Fort, R., Alvarez de Buergo, M., Gomez-Heras, M., Vazquez- Calvo, C. 2006: *Heritage, Weather. Conserv.* **1-2**. – London.
- Giacobini, C., Pietrini, A.M., Ricci, S., Roccardi, A. 1987: Problemi di biodeterioramento, in *Materiali lapidei. Problemi relativi allo studio del degrado e della conservazione*, **1**. – Roma.
- Guiamet, P. S., Gómez de Saravia, S. G., Arenas, P. M., Pérez, M. L., De la Paz, J. N., Borrego, S. 2006: Natural products isolated from plants used in biodeterioration control. – *Pharmacologyonline* **3**: 537-544.
- Guiamet, P. S., De la Paz, J. N., Arenas, P. M., Gómez de Saravia, S. G. 2008: Differential sensitivity of *Bacillus* sp. isolated from archive materials to plant extracts. – *Pharmacologyonline* **3**: 649-658.
- Kovacic, L., 2000: Cyanobacteria and algae as agents of biodeterioration of stone substrata of historical buildings and other cultural monuments. – Pp. 44-58 in: Choi, S. & Suh, M. (eds), *Proceedings of the New Millennium International Forum on Conservation of Cultural Property*. – Daejeon.
- Marzano, A. & Métraux, G. P. R. 2018: *The Roman Villa in the Mediterranean Basin: Late Republic to Late Antiquity*. – Cambridge.
- McCann, M. J., Rowland, I. R., Roy, N. C. 2014: The Anti-Proliferative Effects of Enterolactone in Prostate Cancer Cells: Evidence for the Role of DNA Licensing Genes, mi-R106b Cluster Expression, and PTEN Dosage. – *Nutrients* **6(11)**: 4839-4855. doi: 10.3390/nu6114839
- Mitsch, P., Zitterl-Eglseer, K., Kohler, B., Gabler, C., Losa, R., Zimpernik, I. 2004: The Effect of Two Different Blends of Essential Oil Components on the Proliferation of *Clostridium perfringens* in the Intestines of Broiler Chickens. – *Poultry Sci.* **83(4)**: 669-675. doi: 10.1093/ps/83.4.669
- Noshuyta, W., Osman, E., Mansour, M., 2016: An investigation of the biological fungicidal activity of some essential oils used as preservatives for a 19th century Egyptian Coptic cellulosic manuscript. – *Int. J. Conserv. Sci.* **7(1)**: 41-56.
- Palla, F., Anello, L., Marineo, S., Lombardo, G. 2006: Characterization of bacterial community in indoor environment. – Pp. 361-365 in: Fort, R., Alvarez de Buergo, M., Gomez-Heras, M., Vazquez-Calvo, C.: *Heritage, Weathering and Conservation*. – London.
- Palla, F., Billeci, N., Mancuso, F. P., Pellegrino, L., Lorusso, L. C. 2010: Microscopy and molecular biology techniques for the study of biocenosis diversity in semi-confined environments. – *Conserv. Sci. Cult. Heritage* **10**: 185-194.
- Palla, F. 2012: Analytical techniques. – Pp. 459-470 in: Fabbri, B. (ed.), *Science and Conservation for Museum Collections*, **14**. – Firenze.
- , Barresi, G. 2017: *Biotechnology and Conservation of Cultural Heritage*. – Basingstoke.
- , Mancuso, F. P., Billeci, N. 2013: Multiple approaches to identify bacteria in archaeological waterlogged wood. – *J. Cult- Herit.* **14**: e61-e64. doi: 10.1016/j.culher.2012.11.025
- Pasquarella, C., Pasquariello, G., Balocco, C., Saccani, E., Marmonti, E., Palla, F., Ugoletti, M., Maggi, O., Albertini, R. 2015: Biological and microclimatic diagnosis in cultural heritage conservation: interdisciplinary research at Palatina library in Parma. – *Sci.Total Environ.* **536**: 557-567.

- Reichling, J., Schnitzler, P., Suschke, U., Saller, R. 2009: Essential oils of aromatic plants with anti-bacterial, antifungal, antiviral, and cytotoxic properties—an overview. – *Forsch. Komplementarmed.* **16:** 79-90.
- Roby, T. & Demas, M. 2013: Mosaic in situ. An overview of literature on conservation of mosaics in situ. The Getty Conservation Institute. – Los Angeles
- Rotolo, V., De Caro, M.L., Pasquariello, G., De Nuntiis, P., Palla, F. 2017: Will the plants save art? Potential use of essential oils in Cultural Heritage field. – 2nd Green Conservation of Cultural Heritage – International Conference, Palermo.
- , Barresi, G., Di Carlo, E., Giordano, A., Lombardo, G., Crimi, E., Costa, E., Bruno, M., Palla, F. 2016: Plant extracts as green potential strategies to control the biodeterioration of cultural heritage. – *Intern. J. Conserv. Sci.* **7(2):** 839-846.
- Salem, M. Z. M., Abdel-Megeed, A., Ali H. M. 2014: Stem wood and bark extracts of *Delonix regia* (Boj. ex. Hook): chemical analysis and antibacterial, antifungal, and antioxidant properties. – *BioResources*. **9:** 2382-2395.
- Sanchez-Moral, S., Bedoya, J., Luque, L., Cañaveras, J. C., Jurado, V., Laiz,L., Saiz-Jimenez, C. 2003: Biomineralization of different crystalline phases by bacteria isolated from catacombs.– Pp. 179-185 in: Saiz-Jimenez, C. (ed.), *Molecular Biology in Cultural Heritage*. –Lisse.
- Stupar, M., Lj Grbić, M., Džamić, A., Unković, N., Ristić, M., Jelikić, A., Vukojević, J. 2014: Antifungal activity of selected essential oils and biocide benzalkonium chloride against the fungi isolated from cultural heritage objects. – *South African J. Bot.* **93:** 118-124. doi: 10.1016/j.sajb.2014.03.016
- Tiano, P., Accolla, P. & Tomaselli, L. 1995: Phototrophic biodeteriogens on lithoid surfaces: an ecological studies. – *Microbial Ecol.* **29:** 299-309.
- Warscheid, T., 2000: Integrated concepts for the protection of cultural artifacts against biodeterioration. – Pp. 185-201 in: Ciferri, O., Tiano, P., Mastromei, G. (eds) *Of microbes and Art – The role of microbial communities in the degradation and protection of cultural heritage*. – New York.
- Warscheid, T. H. & Braams, J. 2000: Biodeterioration of stone: a review. – *Intern. Biodeterior. Biodegr.* **46:** 343-368.

Address of the authors:

Valentina Rotolo, Maria Letizia De Caro, Ambra Giordano & Franco Palla,
Department of Biological, Chemical and Pharmacological Sciences and Technology
(STEBICEF), University of Palermo, via Archirafi, 38, 90123 Palermo, Italy.
Corresponding author: Franco Palla, E-mail: franco.palla@unipa.it

